

A crib-shaped triplet pairing gap function for an orthogonal pair of quasi-one dimensional Fermi surfaces in Sr_2RuO_4

Kazuhiko Kuroki,* Masao Ogata, Ryotaro Arita, and Hideo Aoki
Department of Physics, University of Tokyo, Hongo, Tokyo 113-0033, Japan
 (February 1, 2008)

The competition between spin-triplet and singlet pairings is studied theoretically for the tight-binding α - β bands in Sr_2RuO_4 , which arise from two sets of quasi-one dimensional Fermi surfaces. Using multiband FLEX approximation, where we incorporate an anisotropy in the spin fluctuations as suggested from experiments, we show that (i) the triplet can dominate over the singlet (which turns out to be extended s), and (ii) the triplet gap function optimized in the Eliashberg equation has an unusual, very non-sinusoidal form, whose time-reversal-broken combination exhibits a crib-shaped amplitude with dips.

PACS numbers: 74.20-z, 74.20Mn

Spin-triplet superconductivity is of great conceptual importance. It is interesting to ask how the spins in a Cooper pair can align, since usually the singlet pairing is favored so that some special mechanism should be envisaged to account for a triplet superconductivity. The p -wave pairing in superfluid ^3He is an outstanding example, where a clear picture of the hard-core interaction favoring the triplet exists.

In the past several years, Sr_2RuO_4 ¹ has attracted much attention as a strong candidate for triplet superconductivity. In a seminal paper, Rice and Sigrist suggested a mechanism for triplet pairing in this material, which they call an ‘electronic version of He’.² In their scenario the orbital degeneracy causes ferromagnetic spin fluctuations, which is considered to favor the triplet pairing. Subsequent experiments indeed suggested triplet pairing.^{3,4} However, a new puzzle arose when the spin fluctuation in Sr_2RuO_4 was found to be antiferromagnetic rather than ferromagnetic in a neutron scattering experiment.⁵ Usual wisdom dictates that antiferromagnetic spin fluctuations lead to singlet d -wave pairing.⁶

Recently, Kuwabara and one of the present authors,⁷ and independently Sato and Kohmoto,⁸ have proposed that anisotropy in the spin-fluctuation, observed in NMR experiments for Sr_2RuO_4 ,⁹ may lead to triplet p -wave pairing. However, simple functional forms for triplet and singlet gap functions were assumed in ref. 7, i.e., $\sin k_x (+i \sin k_y)$ ¹⁰ for p -wave and $\cos k_x - \cos k_y$ for $d_{x^2-y^2}$ -wave. In ref. 8, the form of the gap when the quasi-1D Fermi surfaces are hybridized was discussed only qualitatively. The form of the gap function is crucial in discussing the triplet-singlet competition, so the functional form should be optimized. The form of the gap function is also important in comparing with experimental results because, e.g., some recent experiments have suggested presence of nodes in the superconducting gap,^{11,12} while a thermal conductivity measurement suggests an isotropic gap.¹³

The purpose of the present paper is to determine the functional form of the superconducting gap func-

tion self-consistently for the spin-anisotropy mechanism mentioned above. We adopt the fluctuation exchange (FLEX) approximation¹⁴, in which we incorporate anisotropy in the spin fluctuations. The FLEX results are then fed into the linearized Eliashberg equation to obtain the gap function. The optimized triplet gap function turns out to have unexpected, non-sinusoidal forms, which are in sharp contrast with the k_x or $\sin k_x$ gap functions assumed previously. As a result, the amplitude of the gap has a shape of a crib along the Fermi surface, which may resolve the controversial experiments. The origin of the peculiar behavior of the gap function is traced back to the singular k -dependence in the spin susceptibility due to a nesting of two sets of quasi-one dimensional Fermi surfaces.

The ruthenate is essentially a three-band system, which arises from d_{xz} orbitals aligned linearly along the x axis, d_{yz} along the y , and d_{xy} in the xy plane. The former two give rise to the α, β bands, which are well nested due to the quasi-one dimensionality and causes antiferromagnetic spin fluctuations. In this paper, we concentrate on the α, β bands, namely, we consider a tight-binding model,

$$H = -t \sum_{\sigma} \sum_{m=xz,yz} \sum_{\langle ii' \rangle}^{\text{nn}} \left(c_{i\sigma}^{m\dagger} c_{i'\sigma}^m + \text{H.c.} \right) - t' \sum_{\sigma} \sum_{\langle i,j \rangle}^{\text{nnn}} \left(c_{i\sigma}^{xz\dagger} c_{j\sigma}^{yz} + \text{H.c.} \right) + U \sum_i \sum_{m=xz,yz} n_{i\uparrow}^m n_{i\downarrow}^m. \quad (1)$$

on a square lattice. Here $c_{i\sigma}^{m\dagger}$ creates an electron at $d_m(m = xz \text{ or } yz)$ orbital. the nearest-neighbor hopping integral t is along the $x(y)$ direction for $d_{xz}(d_{yz})$ orbitals. We take $t = 1$ as a unit of energy.

We have also included the next nearest-neighbor hopping t' which corresponds to a weak hybridization. When $t' \neq 0$ the two sets of quasi-one-dimensional bands anticross, and two two-dimensional (rounded-square) bands result, which are the α and β bands. The on-site repulsive interaction, U , is considered within each orbitals, and in-

terorbital interactions are neglected for simplicity.¹⁵ The band filling is $n = 4/3$ electrons per orbital in Sr_2RuO_4 .

In treating the interaction, we employ the FLEX approximation. This method is a kind of self-consistent random-phase approximation (RPA) where the dressed Green's function is used in the RPA diagrams. In the multiband version of FLEX,^{16,17} the Green's function G , the susceptibility χ , the self-energy Σ , and the superconducting gap function ϕ all become 2×2 matrices, e.g., $G_{lm}(\mathbf{k}, i\epsilon_n)$, where l, m denote d_{yz} or d_{xz} orbitals. The orbital-indexed matrices for Green's function and the gap functions can be converted into band-indexed ones with a unitary transformation. As for the spin susceptibility, we diagonalize the 2×2 matrix χ_{sp}^{zz} and concentrate on the larger eigenvalue, denoted as χ^{zz} .

The actual calculation proceeds as follows:

- (i) Dyson's equation is solved to obtain the renormalized Green's function $G(k)$, where k is a shorthand for the wave vector $\mathbf{k}$ and the Matsubara frequency, $i\epsilon_n$,
- (ii) The fluctuation-exchange interaction $V^{(1)}(q)$ is given as¹⁸

$$V^{(1)}(q) = \frac{1}{2}V_{\text{sp}}^{zz}(q) + V_{\text{sp}}^{+-}(q) + \frac{1}{2}V_{\text{ch}}(q). \quad (2)$$

The effective interactions due to longitudinal (zz) and transverse ($+-$) spin fluctuations (sp) and that due to charge fluctuations (ch) have the forms $V_{\text{sp}}^{zz} = U^2\chi_{\text{sp}}^{zz}$, $V_{\text{sp}}^{+-} = U^2\chi_{\text{sp}}^{+-}$, and $V_{\text{ch}} = U^2\chi_{\text{ch}}$, respectively, where the spin and the charge susceptibilities are

$$\chi_{\text{sp}}^{zz}(q) = \chi^{\text{irr}}(q)[1 - U\chi^{\text{irr}}(q)]^{-1}, \quad (3)$$

$$\chi_{\text{sp}}^{+-}(q) = \alpha\chi^{\text{irr}}(q)[1 - U\alpha\chi^{\text{irr}}(q)]^{-1}, \quad (4)$$

$$\chi_{\text{ch}}(q) = \chi^{\text{irr}}(q)[1 + U\chi^{\text{irr}}(q)]^{-1}, \quad (5)$$

in terms of the irreducible susceptibility $\chi^{\text{irr}}(q) = -\frac{1}{N}\sum_k G(k+q)G(k)$ (N : number of k -point meshes). Here we have taken account of the anisotropy in the spin fluctuation by introducing a phenomenological parameter α à la Kuwabara-Ogata.⁷ From the NMR experiments,⁹ we assume $\alpha < 1$.

(iii) $V^{(1)}$ then brings about the self-energy, $\Sigma(k) = \frac{1}{N}\sum_q G(k-q)V^{(1)}(q)$, which is fed back to Dyson's equation, and the self-consistent iterations are repeated until convergence is attained. We take 64×64 k -point meshes and up to 16384 Matsubara frequencies in order to ensure convergence at low temperatures.

We determine T_c as the temperature at which the eigenvalue λ of the Eliashberg equation,

$$\lambda_\mu \phi_{\mu lm}(k) = -\frac{T}{N} \sum_{k'} \sum_{l', m'} \times V_{\mu lm}^{(2)}(k-k') G_{ll'}(k') G_{mm'}(-k') \phi_{\mu l' m'}(k'), \quad (6) \quad V_\phi = -\frac{\sum_{\mathbf{k}, \mathbf{k}' \in \text{FS}} V_\mu^{(2)}(\mathbf{k}-\mathbf{k}') \phi_\mu(\mathbf{k}) \phi_\mu(\mathbf{k}')}{\sum_{\mathbf{k} \in \text{FS}} [\phi(\mathbf{k})]^2} \quad (10)$$

reaches unity. Here the pairing interaction $V_\mu^{(2)}$ is given by

$$V_s^{(2)} = \frac{1}{2}V_{\text{sp}}^{zz} + V_{\text{sp}}^{+-} - \frac{1}{2}V_{\text{ch}} \quad (7)$$

for singlet pairing,

$$V_{t\perp}^{(2)} = -\frac{1}{2}V_{\text{sp}}^{zz} - \frac{1}{2}V_{\text{ch}} \quad (8)$$

for triplet pairing with $S_z = \pm 1$ ($\vec{d} \perp \vec{z}$), and

$$V_{t\parallel}^{(2)} = \frac{1}{2}V_{\text{sp}}^{zz} - V_{\text{sp}}^{+-} - \frac{1}{2}V_{\text{ch}} \quad (9)$$

for triplet pairing with $S_z = 0$ ($\vec{d} \parallel \vec{z}$). Here $\vec{d}$ is the d -vector characterizing the triplet pairing gap function.

When the electron-electron repulsion, which causes fluctuations, is short-ranged (as for the Hubbard U interaction) the spin fluctuations are much stronger than the charge fluctuations, i.e., ($V_{\text{sp}} \gg V_{\text{ch}}$).¹⁵ When fluctuations for a certain ('nesting') wave vector $\mathbf{Q}$ are pronounced, the main contribution in the summation in eq.(6) comes from those satisfying $\mathbf{k} - \mathbf{k}' \simeq \mathbf{Q}$, which should be the case when the Fermi surface is nested. The present Fermi surface is indeed well nested due to the quasi-one-dimensionality.

Now we turn to the results summarized in Fig.1 for $t' = 0.3$ and $U = 5$. In Fig.1(a), the ridges in $|G|^2$ delineate α and β Fermi surfaces. These quasi-1D surfaces are strongly nested at $\mathbf{q} \equiv (2\pi/3, q_y)$ and $\mathbf{q} \equiv (q_x, 2\pi/3) \pmod{2\pi}$, so that the spin susceptibility is ridged in a crib shape as shown in Fig.1(b), with peaks at the corners, $\mathbf{q} \equiv (\pm 2\pi/3, \pm 2\pi/3)$. This is consistent with neutron scattering experiments.⁵

The triplet and singlet gap functions obtained by solving the Eliashberg equation are shown in Fig.1(c) and (d), respectively. Remarkably, the triplet gap function takes a strange shape: although the symmetry is consistent with p -wave, its form is far from $\sin k_x$ along the rounded-square Fermi surface. Rather, it has an almost constant amplitude on a pair of parallel sides, $k_x \equiv \pm 2\pi/3 \pmod{2\pi}$, of the square with a *vanishing* amplitude on the other pair ($k_y \equiv \pm 2\pi/3$) of parallel sides. This applies to each of the α and β bands. Of course the symmetry dictates that the other solution (p_y), rotated by 90 degrees from what is described here (p_x), enters on an equal footing as we shall discuss below.

Why do we have this peculiar behavior for the FLEX+Eliashberg optimized gap function? To begin with, superconductivity arises due to pair scattering from $(\mathbf{k}, -\mathbf{k})$ to $(\mathbf{k}', -\mathbf{k}')$ mediated by the pairing interaction $V^{(2)}(\mathbf{q})$, where $\mathbf{q} = \mathbf{k} - \mathbf{k}'$ is the momentum transfer. From the BCS gap equation we can see that superconductivity arises if the quantity

is positive and large, where we denote the gap function as ϕ_μ ($\mu = s$ for singlet and t for triplet pairing).

As discussed by Kuwabara and Ogata⁷, and independently by Sato and Kohmoto⁸, the p -wave pairing, with $\phi_t(\mathbf{k})\phi_t(\mathbf{k} + \mathbf{Q}) < 0$, is favored when spin anisotropy is so strong as to realize $V_{sp}^{zz}(\mathbf{Q}) > 2V_{sp}^{+-}(\mathbf{Q})$, i.e., $V_{t\parallel}(\mathbf{Q}) > 0$. However, the present self-consistent calculation shows that the situation is a little more involved. A key factor is the spin fluctuation that is enhanced along a line

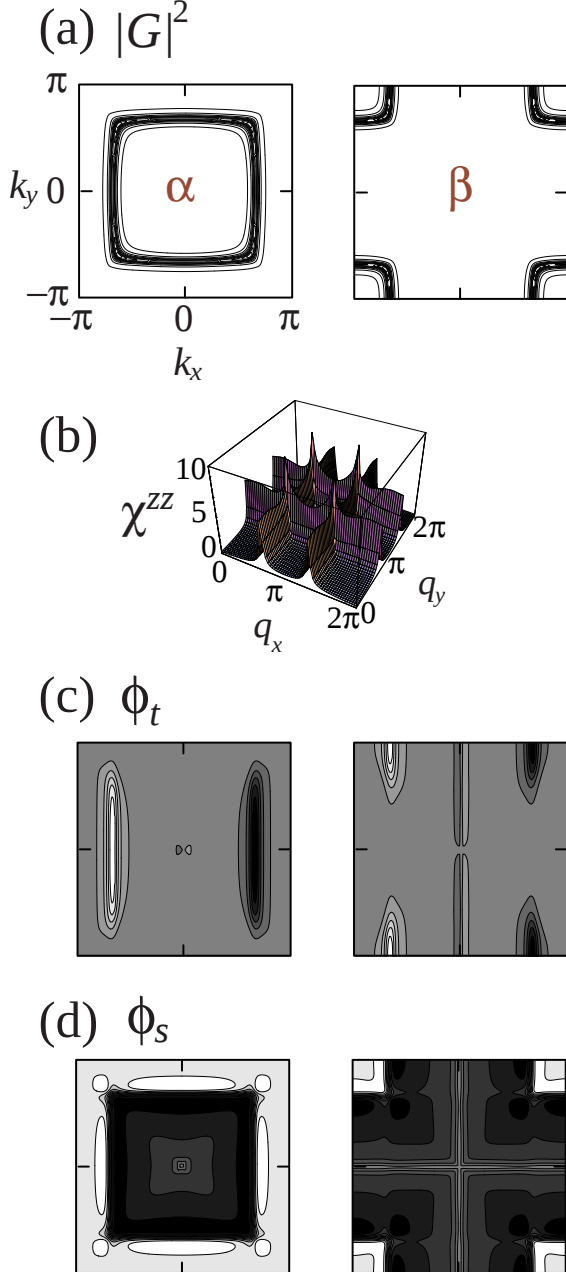


FIG. 1. The contour plot of the FLEX result for Green's function ($|G|^2$; a), spin susceptibility (b), optimized gap function for the spin triplet (ϕ_t ; c) or singlet (ϕ_s ; d) pairing for $U = 5$, $t' = 0.3$, $\alpha = 0.8$, and $T = 0.02$. The left(right) panel for the $\alpha(\beta)$ band, and white(black) corresponds to positive(negative) amplitude in (c,d).

$\mathbf{q} \equiv (q_x, 2\pi/3)$. For a given nodal line (vertical for p_x pairing), the pair scatterings across one pair of parallel sides of the Fermi surface become all favorable as indicated by $\circ$ in Fig.2(a). This gives rise to the near-constant gap function on that pair of sides of the Fermi surface. By contrast, the pair scatterings across the other pair of parallel sides ($\times$ in Fig.2(a)) lead to

$$-V_t^{(2)}(k_x - k'_x, -\frac{2\pi}{3} - \frac{2\pi}{3})\phi_t(k_x, -\frac{2\pi}{3})\phi_t(k'_x, \frac{2\pi}{3}) < 0$$

in eq.(10) when k_x, k'_x have the same sign. Since $-V_t^{(2)}$ is negative, the p_x -wave gap functions on these sides of the Fermi surface is unfavored. This explains the gap function shown in Fig.1(c).

Now, let us move on to the competing superconducting state in the singlet channel. Although Kuwabara and Ogata discussed a competition between the triplet p_x -wave and a singlet $d_{x^2-y^2}$ -wave, we find here that the real competitor (the most stable singlet state) is unexpectedly an extended s -wave rather than $d_{x^2-y^2}$ -wave. This is understood as follows. Since $V_s(\mathbf{Q}) > 0$ is repulsive, $\phi_s(\mathbf{k})\phi_s(\mathbf{k} + \mathbf{Q}) < 0$ has to be satisfied. For the $d_{x^2-y^2}$ -wave, the $\mathbf{k}, \mathbf{k}' = \mathbf{k} + \mathbf{Q}$ on the Fermi surface that

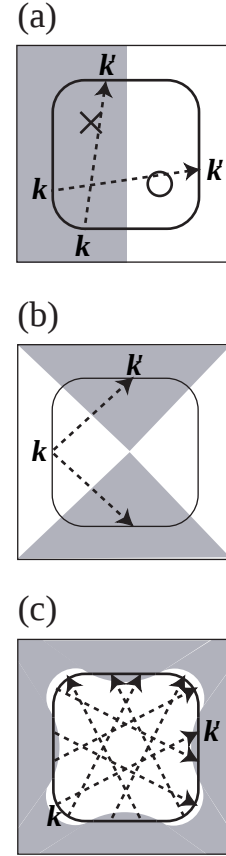


FIG. 2. Pair scatterings across the Fermi surface which favor ($\circ$) or unfavor ($\times$) p_x -wave pairing (a), those contributing to $d_{x^2-y^2}$ (b) or to extended s pairings (c). The white(grey) areas represent positive(negative) ϕ .

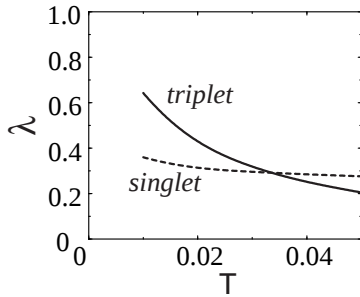


FIG. 3. Eigenvalues of the Eliashberg equation for triplet and singlet pairings as a function of temperature for $U = 5$, $t' = 0.3$, $\alpha = 0.8$.

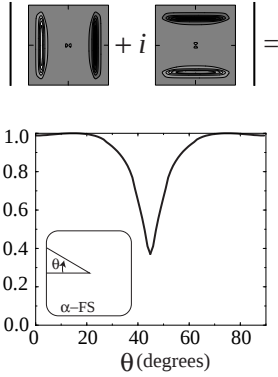


FIG. 4. $|\phi(\mathbf{k})|$ (eq.(11)) for $U = 5$, $t' = 0.3$, $\alpha = 0.8$, and $T = 0.02$. The inset shows how the two functions are combined.

satisfy $\mathbf{k} - \mathbf{k}' \sim (\pm 2\pi/3, \pm 2\pi/3) \pmod{2\pi, 2\pi}$ and $\phi_s(\mathbf{k})\phi_s(\mathbf{k}') < 0$ are only $\mathbf{k}, \mathbf{k}' \sim (\pm 2\pi/3, 0), (0, \pm 2\pi/3)$ (dashed arrows in Fig.2(b)). By contrast, all the $\mathbf{k}, \mathbf{k}'$'s on the Fermi surface with $\mathbf{k} - \mathbf{k}' \sim (\pm 2\pi/3, \pm 2\pi/3)$ contribute to the extended s-wave pairing (Fig.2(c)).

The competition between the triplet and singlet is quantified by the eigenvalues of the Eliashberg equation, shown in Fig.3 as functions of temperature.¹⁹ It can be seen that for the value of $\alpha (= 0.8)$ adopted here, the triplet does dominate at low temperatures. The singlet extended-s, although having a greater magnitude of the pairing interaction, has the nodal line running in the vicinity of the Fermi surface (Fig.1(d)), which should be why this pairing is weaker. If we extrapolate λ to $T \rightarrow 0$ a finite transition temperature much smaller than $O(0.01t)$ is suggested.

The above result and argument are for the p_x -wave. Obviously, the p_y -wave should be degenerate with it from symmetry. A complex linear combination of these two, $p_x + ip_y$, which breaks the time reversal symmetry, should be the true state below T_c since the superconducting gap is maximized for that combination.

The absolute value of the gap function for that linear combination on the Fermi surface,

$$|\phi(\mathbf{k})| = [\phi_t(k_x, k_y)^2 + \phi_t(k_y, k_x)^2]^{1/2}, \quad (11)$$

along the Fermi surface is displayed in Fig.4, which has a crib shape with dips at the corners around $\mathbf{k} \equiv (\pm 2\pi/3, \pm 2\pi/3)$.²⁰ The dip arises because ϕ_t in each of the p_x and p_y channels has already sharp drops at the corner of the Fermi surface. Thus, in phase-insensitive experiments, the gap function obtained here may look like a two-dimensional f -wave pairing with nodes along $k_x = \pm k_y$, since a dip and a node are indistinguishable when the temperature is greater than the dip. Further study on this point is under way.

Discussions with Yuji Matsuda are gratefully acknowledged. This work is in part funded by the Grant-in-Aid for Scientific Research from the Ministry of Education of Japan.

* Present address: Department of Applied Physics and Chemistry, University of Electro-Communications, 1-5-1 Chofugaoka, Chofu-shi, Tokyo 182-8585, Japan

¹ Y. Maeno, H. Hashimoto, K. Yoshida, S. NishiZaki, T. Fujita, J.G. Bednorz, and F. Lichtenberg, Nature **372**, 532 (1994).

² T.M. Rice and M. Sigrist, J. Phys. Cond. Matt. **7**, L643 (1995).

³ G.M. Luke, Y. Fudamoto, K.M. Kojima, M.I. Larkin, J. Merrin, B. Nachumi, Y.J. Uemura, Y. Maeno, Z.Q. Mao, Y. Mori, H. Nakamura, and M. Sigrist, Nature **394**, 558 (1998).

⁴ K. Ishida, H. Mukuda, Y. Kitaoka, K. Asayama, Z.Q. Mao, Y. Mori, and Y. Maeno, Nature **396**, 658 (1998).

⁵ Y. Sidis, M. Braden, P. Bourges, B. Hennion, S. NishiZaki, Y. Maeno, and Y. Mori, Phys. Rev. Lett. **83**, 3320 (1999).

⁶ A competition between p -wave pairing mediated by ferromagnetic spin fluctuations and d -wave pairing by antiferromagnetic fluctuations was discussed by I.I. Mazin and D.J. Singh in Phys. Rev. Lett. **82**, 4324 (1999).

⁷ T. Kuwabara and M. Ogata, Phys. Rev. Lett. **85**, 4586 (2000).

⁸ M. Sato and M. Kohmoto, J. Phys. Soc. Jpn. **69**, 3505 (2000).

⁹ H. Mukuda, K. Ishida, Y. Kitaoka, K. Asayama, Z.Q. Mao, Y. Mori, and Y. Maeno, J. Phys. Soc. Jpn. **67**, 3945 (1998).

¹⁰ This form of the gap function was proposed in K. Miyake and O. Narikiyo, Phys. Rev. Lett. **83**, 1423 (1999).

¹¹ S. NishiZaki, Y. Maeno, and Z.Q. Mao, J. Phys. Soc. Jpn. **69**, 572 (2000).

¹² K. Ishida, H. Mukuda, Y. Kitaoka, Z.Q. Mao, Y. Mori, and Y. Maeno, Phys. Rev. Lett. **84**, 5387 (2000).

¹³ Y. Matsuda, private communications.

¹⁴ N.E. Bickers, D.J. Scalapino, and S.R. White, Phys. Rev. Lett. **62**, 961 (1989); G. Esirgen and N.E. Bickers, Phys. Rev. B **55**, 2122 (1997).

¹⁵ T. Takimoto, Phys. Rev. B **62**, R14641 (2000), has considered interorbital repulsions, which enhances orbital fluctuations to result in a triplet superconductivity.

- ¹⁶ S. Koikegami, S. Fujimoto, and K. Yamada, J. Phys. Soc. Jpn. **66**, 1438 (1997).
- ¹⁷ H. Kontani and K. Ueda, Phys. Rev. Lett. **80**, 5619 (1998).
- ¹⁸ In eqs.(2),(7) –(9) we have omitted the first- and second-order terms, U and $-U^2\chi_0$ (in eq.2), which are negligible when spin and/or charge fluctuations are strong, although we have taken those terms into account in the actual calculation.
- ¹⁹ The simultaneous enhancement of the triplet pairing and the spin fluctuations is reminiscent of the Tomonaga-Luttinger theory for purely 1D systems, where one can show that the susceptibilities for the triplet pairing and the SDW may diverge simultaneously for $T \rightarrow 0$ when the

SU(2) symmetry in the interaction is broken. However, in the Tomonaga-Luttinger case, the triplet pairing dominates over the SDW only when the electron-electron interaction is attractive, in sharp contrast with the present case where the interaction is repulsive. The difference comes from a different origin of the broken SU(2) here, which is the anisotropy in the irreducible susceptibility (which arises at a single electron level) rather than the anisotropic electron-electron interaction.

- ²⁰ We note that, while the qualitative result does not depend crucially on t' (= 0.3 in this paper), the quantitative shape of the dip does.